

Journal of Materials Research

<http://journals.cambridge.org/JMR>

Additional services for *Journal of Materials Research*:

Email alerts: [Click here](#)

Subscriptions: [Click here](#)

Commercial reprints: [Click here](#)

Terms of use : [Click here](#)



Crosslinked SPEEK membranes: Mechanical, thermal, and hydrothermal properties

Hongying Hou, Brunella Maranesi, Jean-François Chailan, Mustapha Khadhraoui, Riccardo Polini, Maria Luisa Di Vona and Philippe Knauth

Journal of Materials Research / Volume 27 / Issue 15 / 2012, pp 1950 - 1957

DOI: 10.1557/jmr.2012.151

Link to this article: http://journals.cambridge.org/abstract_S0884291412001513

How to cite this article:

Hongying Hou, Brunella Maranesi, Jean-François Chailan, Mustapha Khadhraoui, Riccardo Polini, Maria Luisa Di Vona and Philippe Knauth (2012). Crosslinked SPEEK membranes: Mechanical, thermal, and hydrothermal properties. Journal of Materials Research, 27, pp 1950-1957 doi:10.1557/jmr.2012.151

Request Permissions : [Click here](#)

Crosslinked SPEEK membranes: Mechanical, thermal, and hydrothermal properties

Hongying Hou

Laboratoire Chimie Provence (UMR 6264), Centre St Jérôme, Aix-Marseille Univ - CNRS, 13397 Marseille, France

Brunella Maranesi

Laboratoire Chimie Provence (UMR 6264), Centre St Jérôme, Aix-Marseille Univ - CNRS, 13397 Marseille, France; and Dip. Scienze e Tecnologia Chimiche, Univ Roma Tor Vergata, 00133 Roma, Italy

Jean-François Chailan

Univ Sud Toulon-Var, MAPIEM (EA 3834), 83402 La Garde, France

Mustapha Khadhraoui

Laboratoire Chimie Provence (UMR 6264), Centre St Jérôme, Aix-Marseille Univ - CNRS, 13397 Marseille, France

Riccardo Polini and Maria Luisa Di Vona^{a)}

Dip. Scienze e Tecnologia Chimiche, Univ Roma Tor Vergata, 00133 Roma, Italy

Philippe Knauth^{a), b)}

Laboratoire Chimie Provence (UMR 6264), Centre St Jérôme, Aix-Marseille Univ - CNRS, 13397 Marseille, France

(Received 11 January 2012; accepted 30 April 2012)

The thermal and mechanical behavior, the water uptake (WU), and water diffusion coefficient of sulfonated poly(ether ether ketone) (SPEEK) membranes annealed at 180 °C for different times were explored by high-resolution thermogravimetric analysis, mechanical tensile tests, dynamic mechanical analysis, and WU measurements. The mechanical and thermal stability increased with the thermal treatment time, i.e., with the degree of crosslinking. The effect of residual casting solvent, dimethyl sulfoxide (DMSO), on the WU within SPEEK was probed. In presence of residual DMSO, crosslinked SPEEK exhibited higher water sorption at low and medium relative humidity (RH), and lower water sorption at high RH. These membranes have properties well adapted to fuel cell applications.

I. INTRODUCTION

Sulfonated poly(ether ether ketone) (SPEEK), the most important sulfonated aromatic polymer (SAP), is widely considered as a promising polymer electrolyte for proton exchange membrane fuel cells (PEMFC) because of its many advantages such as a low cost, an easy availability, a sufficient proton conductivity, a low fuel permeability.^{1–5} Like for Nafion membranes, the proton conductivity of SPEEK is water dependent and increases with the water content within the membrane.^{6,7} However, the water is like a double-edged sword: on the one hand, a large water content can enable the microphase separation and thus the formation of nanochannels for proton transport; on the other hand, water can also deteriorate mechanical properties of SPEEK, especially for polymers with a high degree

of sulfonation (DS).⁸ In addition, the rather harsh environment during PEMFC operation, combining strong acid and strong oxidizing or reducing conditions, and cyclic variations of temperature and humidity, can aggravate the degradation.^{9–12} How to achieve a better compromise among the proton conductivity, mechanical and thermal stability remains therefore a big challenge.

Different strategies have been developed to solve this problem. First, reinforced materials, such as polytetrafluoroethylene,^{13,14} inorganic carbon fibers,¹⁵ ceramic oxides,¹⁶ or silanol moieties,¹⁷ were introduced into the polymer matrix to improve its mechanical, thermal, and structural stability. The stabilization effect can be owed to the reinforcement by additives and intermolecular interactions between the polymer and other components. Inter/intramolecular crosslinking of macromolecular chains is an alternative strategy.¹⁸ The studies include ionic,^{19,20} covalent,^{21–24} or mixed ionic and covalent crosslinks.^{25–28} The formation of covalent crosslinks (XL) between macromolecular chains allows improving the resistance to solvents, the dimensional stability, and the mechanical strength, while maintaining a locally high density of functional groups, such as sulfonic acid groups.^{29–31} The possibility to perform a direct in situ XL

^{a)}These authors were editors of this focus issue during the review and decision stage. For the *JMR* policy on review and publication of manuscripts authored by editors, please refer to <http://www.mrs.org/jmr-editor-manuscripts/>

^{b)}Address all correspondence to this author.

e-mail: philippe.knauth@univ-amu.fr

DOI: 10.1557/jmr.2012.151

reaction is an additional interesting feature to obtain stable long life membranes. The introduction of a certain number of covalent bonds between adjacent polymeric chains by thermal treatments of cast membranes is really economic. Due to its simplicity, this method is very suitable for a large-scale industrial production of crosslinked membranes because the procedure can be easily upscaled.

The temperature-promoted and solvent-assisted crosslinking of SPEEK membranes was achieved by electrophilic aromatic substitution reactions of sulfonic acid moieties with aromatic rings within the SPEEK matrix. An initial high ion exchange capacity (IEC) can guarantee enough $-\text{SO}_3\text{H}$ groups for proton transport, if the XL density is not too high and not too much $-\text{SO}_3\text{H}$ are affected during the crosslink reaction. As casting solvent, high boiling dimethyl sulfoxide (DMSO) plays an important role in thermal XL reactions because other casting solvents such as N-methylpyrrolidone and dimethylformamide disable the XL reaction under the same conditions.³² In this work, SPEEK membranes with high initial IEC were synthesized and thermally treated for different times (0–24 h). The obtained membranes were characterized in terms of high-resolution thermogravimetric analysis (TGA), mechanical tensile tests, dynamic mechanical analysis (DMA), and water uptake (WU) measurements. In addition, the effect of DMSO on WU, membrane swelling, and water diffusion coefficients was explored. The aim was to show that thermal treatments performed above 150 °C can significantly improve the thermal stability, hydration numbers, and mechanical properties. These results are of significant importance for the improvement of proton exchange membranes for fuel cells.

II. EXPERIMENTAL

A. Materials

Polyether-ether-ketone (PEEK; Victrex, Lancashire, UK, 450 P, MW = 38,300) and other chemicals (Aldrich, Milano, Italy) were reagent grade and were used as received.

B. Sample preparation

The synthesis of SPEEK with a DS in the range of 0.8–1.0 was already reported.³² SPEEK membranes were obtained by the dissolution of SPEEK powder (250 mg) in DMSO (30 mL); the resultant solution was stirred for 4 h, concentrated to 5 mL, and then cast onto a Petri dish at 120 °C for 24 h (first treatment). After cooling to room temperature, resulting membranes were peeled off. To evaluate the effect of the thermal treatment time on membrane properties, the membranes were heated at 180 °C for 3, 10, and 24 h (second treatment).

C. Sample characterization

1. High-resolution TGA

The thermal stability of membranes was evaluated between 30 and 650 °C by high-resolution TGA on a thermal

analyzer (Q500; TA Instruments, Newcastle, DE) in platinum sample holders with about 7-mg sample. The maximum heating rate was 5 °C/min with sample purge (air) at 60 mL/min and balance purge (argon) at 40 mL/min.

2. Determination of IEC

The IEC (milliequivalents of sulfonic groups per gram of dry polymer) was determined by acid–base titrations. To eliminate DMSO and its decomposition products before the titration, the membranes were swelled in water at 100 °C for 5 h then treated with H_2SO_4 5 M at room temperature for 2 h and finally washed again in water. The titration was performed as follows: H-form samples with given dry weight were soaked in 1.5 M NaCl solutions overnight to exchange H^+ with Na^+ ; the protons were titrated with 0.020 M NaOH solutions. The IEC was calculated using the dry weight of the sample and the quantity of exchanged protons.

3. Mechanical tensile tests

Mechanical properties of samples were measured at ambient temperature and relative humidity (RH) (~43%, measured by a humidity sensor) on an Adamel-Lhomargy tensile test machine (M250-2.5 CT; Lhomargy, Paris, France). Samples were cut into small pieces with 5 mm width and 25 mm length and their ends were hold with adhesive tape to optimize mechanical tests. The constant crosshead speed was about 5 mm/min during the test. To evaluate the effect of humidity on mechanical properties, samples were also tested under dry conditions, while keeping other conditions constant. In this case, samples were dried over P_2O_5 for 3 days before the test.

4. DMA

DMA was performed from 30 to 250 °C in air on a DMA 2980 dynamic mechanical analyzer (TA Instruments). Measurements were operated in air at a fixed frequency of 1 Hz with 0.05 N initial static force and oscillation amplitude of 10 μm . This last value was chosen to keep the linear viscoelastic response of samples during experiments. The storage (E') and damping (Tan Delta) spectra versus temperature were obtained at 3 K/min. DMA analysis allows deriving the glass transition temperature of samples treated for different times at 180 °C.

5. Water vapor uptake measurements

The WU was measured by monitoring the weight of samples in water vapor with different activities at 25 °C. Water activities can be controlled in a closed vessel by gas phase equilibrium with P_2O_5 ($a_{\text{H}_2\text{O}} \approx 0$) or different saturated solutions as listed in Table I.³³ Measurements were made at the steady state (240 h) of stabilization. The

TABLE I. Water activity of different saturated salt solutions at room temperature.³³

Saturated salt solution	LiCl	MgCl ₂	NaBr	KBr	H ₂ O
Water activity (RH%)	15	41	58	79	97

saturation was achieved by mixing a large excess of each salt with deionized water.³⁴ Before the experiments, membranes were dried 240 h over P₂O₅ and a final measurement was made in presence of pure water.

Furthermore, water vapor sorption isotherms as function of time were recorded at ambient humidity. To probe the effect of DMSO, residual DMSO within SPEEK was removed by the following procedure: (i) heating in 1 M HNO₃ at 100 °C for 2 h; (ii) rinsing with pure water several times; (iii) heating in pure water at 100 °C for 5 h; (iv) drying the sample in the oven at 120 °C for 15 h.

6. Proton conductivity measurements

The conductivity of membranes was measured as function of RH in a homemade apparatus by two-electrode impedance spectrometry, as described in Ref. 35. Commercial electrodes were used and the through-plane conductivity was obtained from the resistance of membranes and their thickness.

III. RESULTS AND DISCUSSION

A. High-resolution TGA

Figure 1 shows TGA curves of SPEEK heated at 180 °C for 0, 3, 10, and 24 h. The thermal stability of SPEEK increased with the thermal treatment time, and especially for SPEEK annealed for 24 h, the main chain decomposition temperature was higher than those of other samples, indicating that the degree of XL of SPEEK increased with the treatment time,²⁹ forming a more and more dense three-dimensional network.

The DS can be calculated by TGA from the weight loss, Δm , corresponding to desulfonation.²⁹ The DS can be calculated using the following Eq. (1)

$$DS = \frac{n(\text{SO}_3\text{H})}{n(\text{PEEK})} = \frac{M(\text{PEEK})}{\left(\frac{m}{\Delta m} - 1\right)M(\text{SO}_3\text{H})}, \quad (1)$$

where m is the mass of SPEEK, $M(\text{PEEK})$ is the molecular mass of the repeat unit of PEEK (288.7 g/mol), and $M(\text{SO}_3\text{H})$ that of sulfonic acid groups (80.1 g/mol).

Furthermore, the degree of crosslinking (DXL) of SPEEK can be calculated by Eq. (2):

$$\text{DXL} = \frac{DS^\circ - DS}{DS^\circ}. \quad (2)$$

DS° and DS are the degrees of sulfonation of SPEEK before and after the crosslinking reaction, respectively.

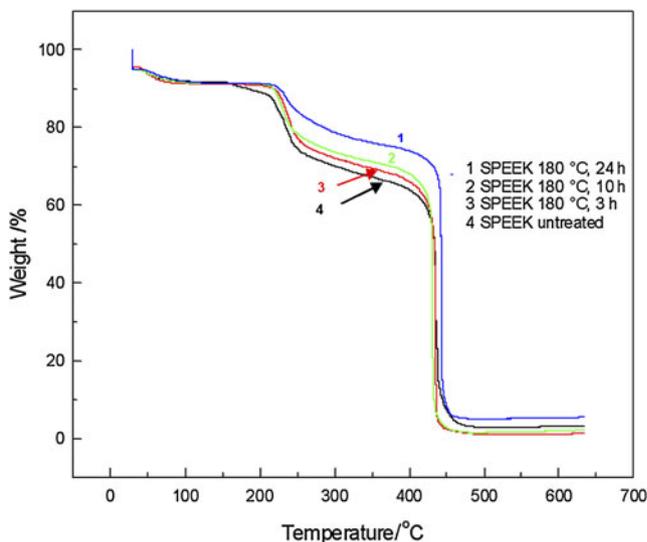


FIG. 1. TGA curves of SPEEK treated at 180 °C for 0, 3, 10, and 24 h.

The calculated DS for different samples are reported together with those by acid–base titrations and with DXL in Table II. There is a good consistency between DS values from TGA and titration.

B. Mechanical tensile tests

Typical stress–strain curves of SPEEK membranes treated at 180 °C for 0, 3, 10, and 24 h, recorded at ambient RH and 0% RH, are shown in Fig. 2. The corresponding mechanical properties [Young modulus, yield stress, ultimate tensile strength (UTS), and elongation at break] are listed in Table III and are plotted versus DXL in Fig. 3. The mechanical properties of samples increase with the treatment time. In the presence of water, the Young modulus increases from 850 to 1450 MPa with increasing DXL values. In dry conditions, the change is much smaller. In both cases, the Young modulus seems to reach a plateau value around 1450 MPa above DXL 0.3. This property reflects the stiffness of the polymer and explores low displacements on microscopic scale of bond lengths or bond angles, i.e., elastic deformation, and essentially weak bonds. In wet conditions, the presence of water between macromolecular chains reduces strongly the van der Waals bonds; the water molecules act as plasticizer. This is the reason of the much higher Young modulus in dry conditions. Increasing DXL reduces and fixes the mean distance between macromolecules. The reticulation restricts chains from sliding past one another and generates higher elasticity in amorphous polymers. The Young modulus increases thus strongly with increasing DXL in humid conditions.

The yield stress, the UTS, and the elongation at break reflect instead larger unrecoverable displacements (plastic deformation) along the chain length direction, generally corresponding to initial orientating movements of the

TABLE II. Calculated DS from TGA and titration and DXL.

Sample	TGA	Titration	
	DS (%)	DS (%)	DXL ^{a)} (%)
Untreated SPEEK (at 180 °C for 0 h)	86	90	0
Treated SPEEK at 180 °C for 3 h	75	84	10
Treated SPEEK at 180 °C for 10 h	66	68	24
Treated SPEEK at 180 °C for 24 h	49	45	47

^{a)}The average DS from TGA and titration is used for the calculation of DXL according to Eq. (2).

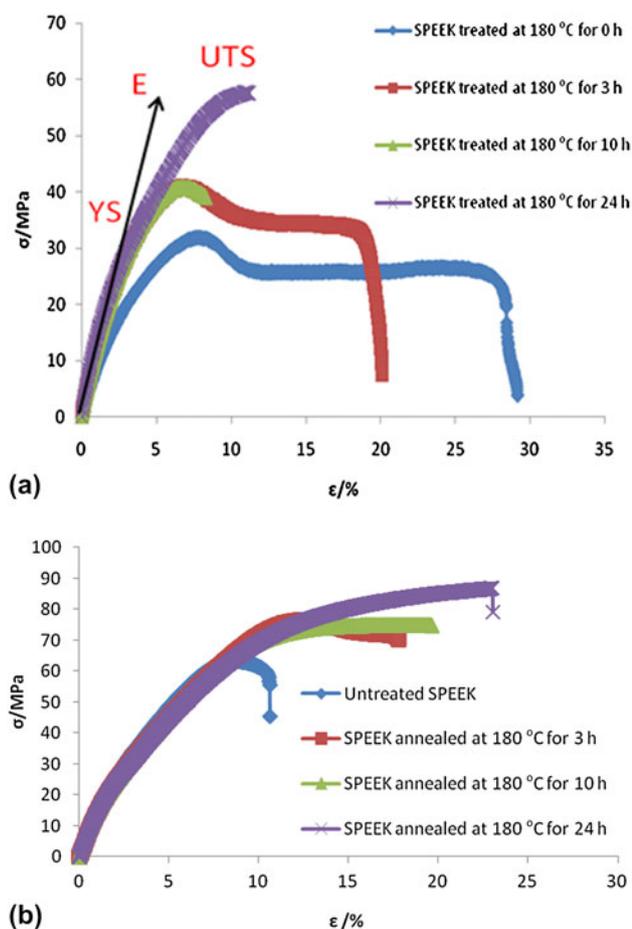


FIG. 2. Typical stress–strain curves of SPEEK treated at 180 °C for different times and different RH (a: ambient 43% RH; b: 0% RH).

TABLE III. Mechanical properties of SPEEK samples (E: elastic modulus).

Sample	E (MPa)		UTS (MPa)		YS (MPa)		Elongation at break (%)	
	43% RH	0% RH	43% RH	0% RH	43% RH	0% RH	43% RH	0% RH
Untreated SPEEK 180 °C 0 h	850 ± 60	1461	32 ± 1	63	20 ± 5	55	20 ± 8	11
SPEEK treated 180 °C 3 h	1160 ± 50	1553	41 ± 2	76	30 ± 5	65	22 ± 9	18
SPEEK treated 180 °C 10 h	1300 ± 100	1590	43 ± 8	75	40 ± 5	62	20 ± 12	20
SPEEK treated 180 °C 24 h	1450 ± 50	1526	59 ± 2	87	45 ± 5	70	11 ± 1	23

polymer chains (yield stress) and final collapse of the original polymer microstructure (elongation at break). These properties probe the strong covalent bonds inside the macromolecules. The multidirectional extension of polymer chains corresponding to XL induced by the heat treatment leads to the formation of network structures and restricts the viscous flow. The effects of reticulation on mechanical properties of SPEEK are strongly influenced by the regularity of the network formed during heat treatments. A higher crosslinking leads to a significant increase of the yield stress and tensile strength by limiting the movement of chain segments and decreasing the flexibility. The stiffness or rigidity of polymers becomes higher and the elongation at break decreases. The network structure gives the polymer a high-dimensional stability and mechanical strength.

In humid atmosphere, the presence of water enlarges the distance between polymer chains reducing the interaction among them and thus the mechanical strength of the polymer (plasticizing effect). The yield stress and UTS are therefore consistently higher for the dry polymer. Inter- and intramolecular crosslinks lead to a significant improvement of properties in all cases as supplementary strong covalent bonds are formed. The satisfying mechanical properties indicate a promising potential for PEMFC application under high temperature and low RH conditions.

C. DMA

DMA curves (Fig. 4) allow determining storage modulus values through a large temperature range and glass transition temperatures (T_g) of SPEEK polymers.³⁶ This technique can also give interesting qualitative information on crosslinking degree.

From a quantitative point of view, storage modulus values in the glassy state are consistent with the elastic modulus from tensile tests; the storage modulus of SPEEK increases with the treatment time at 180 °C, due to increasing DXL [Fig. 4(a)], as discussed previously. The α relaxation temperature obtained from the Tan δ peak maximum can be assimilated to the glass transition temperature T_g . This temperature also increases with the annealing time due to a symmetry reduction by crosslinking [Fig. 4(b)].

From a qualitative point of view, one can note that during α relaxation, the decrease of storage modulus is inversely proportional to the treatment time. For uncrosslinked and low crosslinked SPEEK samples, this decrease is followed

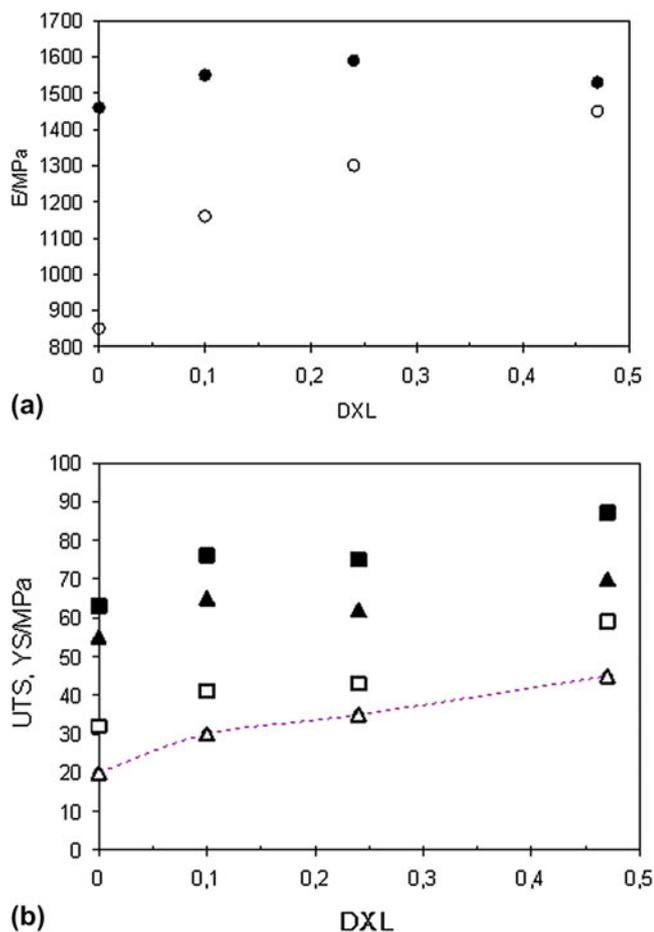


FIG. 3. Young modulus (E), yield strength (YS), and UTS as a function of DXL of SPEEK under 43% (empty dots) and 0% RH (solid dots).

by an increase in the rubbery state. This increase is due to the sample stiffening with temperature, probably by crosslink reactions occurring with remaining $-\text{SO}_3\text{H}$ groups. During DMA experiments, samples are subjected simultaneously to high temperature (over 180°C) and mechanical stress, which act as an accelerated thermal treatment. This phenomenon is similar to the well-known thermoset post-reticulation commonly observed in DMA experiments. In addition and in agreement with previously results, the longest thermal treatment at 180°C (24 h) seems to give the maximum crosslink since no storage modulus increase is observed in the rubbery state for this sample.

D. WU and effect of residual DMSO

The WU of membranes is an important property for fuel cell applications. The WU is defined as:

$$\text{WU} = \frac{m(\text{wet}) - m(\text{dry})}{m(\text{dry})} \quad (3)$$

Here, $m(\text{wet})$ is the mass of the wet and $m(\text{dry})$ the mass of the dry membrane sample. The WU determination is not

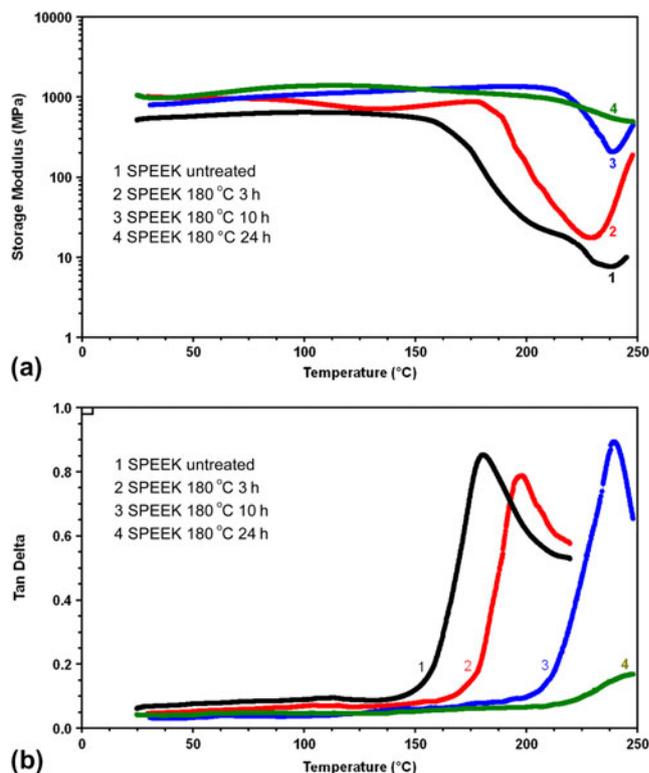


FIG. 4. DMA results of SPEEK treated at 180°C for 0, 3, 10, 24 h. (a) Storage modulus versus temperature and (b) T_g versus temperature.

trivial because the membrane preparation and history play an important role. For example, the WU reported for XL sulfonated polyimide was higher than that before crosslinking, due to the large free space within the polymer matrix created by long chains of crosslinker molecules.³⁷

Our measurements were conducted for very long times (240 h) to achieve steady-state conditions because it was shown that very slow changes of conformations can modify the WU and lead to some of the unexplained divergences between literature data.³⁸

The measured WU is also very sensitive to the presence of residual DMSO in the membranes. Considering the high boiling point and the interaction of DMSO with $-\text{SO}_3\text{H}$ groups,³⁹ there is still residual DMSO within SPEEK even heated at 180°C for some time.^{29,30} This is why we compared membranes with residual DMSO and those where the residue was completely and carefully removed by treatment in 1 M HNO_3 and pure water at 100°C . By comparing dry weights of SPEEK before and after this treatment, we could estimate the quantity of residual DMSO within SPEEK. The data listed in Table IV show that the amount of residual DMSO decreased with the annealing time. It is reasonable to infer that DMSO reduces the amount of absorbed water by obstructing the channels, and evidence of this hypothesis is provided in the following.

Figure 5 shows the water vapor uptake from $\approx 0\%$ to 97% RH before and after the removal of residual DMSO.

TABLE IV. Storage modulus, glass transition temperature T_g , quantity of residual DMSO, and chemical diffusion coefficients of water D .

Sample	Storage modulus (MPa)	T_g (°C)	Quantity of DMSO (wt%)	$D \times 10^9$ (cm ² /s)
SPEEK annealed 180 °C 0 h	600	180	5.5	9.1
SPEEK annealed 180 °C 3 h	800	193	5.0	6.7
SPEEK annealed 180 °C 10 h	1300	239	1.5	7.0
SPEEK annealed 180 °C 24 h	1400	241	1.3	4.7



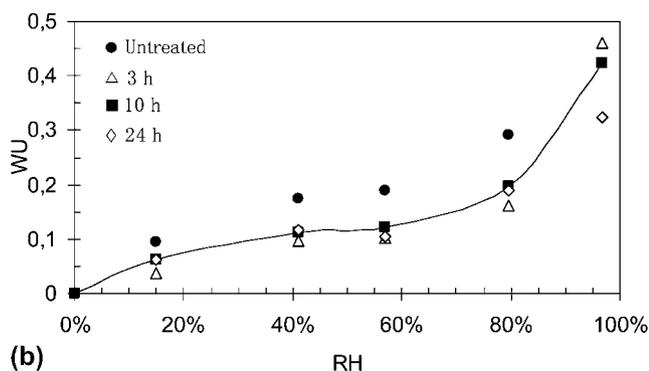


FIG. 5. WU curves of SPEEK treated at 180 °C for 0, 3, 10, and 24 h as a function of RH (0–97%), (a) with residual DMSO and (b) without residual DMSO.

The water vapor uptake of all samples increased slowly at low and medium RH, while quickly at high RH, which corresponds to hydration and swelling of membranes, respectively.⁴⁰ Though a sufficient WU at low RH is mandatory for proton conductivity, a too high WU at high RH must be avoided to limit membrane swelling. By comparing Figs. 5(a) and 5(b), the effect of residual DMSO on the water vapor uptake can be observed. At low and medium RH, treated SPEEK exhibited slightly higher water vapor uptakes than untreated SPEEK. The reason is the residual solvent within the membranes, considering that DMSO is an aprotic polar solvent with a strong affinity for water.³⁵ The low free space within untreated SPEEK, caused by the

presence of DMSO interacting with $-\text{SO}_3\text{H}$ groups, limits the capacity to absorb water; this results in a lower WU than that without DMSO. The thermal treatment at 180 °C is accompanied by partial removal of DMSO by evaporation so that more free space is available for water. This leads to the apparently paradoxical result that the WU of treated membranes at low RH is higher than for untreated ones. After removal of residual DMSO, the water vapor uptake of treated SPEEK is lower than that of untreated SPEEK within the entire RH range, as expected [Fig. 5(b)]. The sample treated 3 h presents apparently the lowest WU at low RH; maybe some residual DMSO is trapped inside this membrane.

At low and medium RH, the effective water activity in the gas phase is low, and there is no strong thermodynamic driving force, which enables DMSO to escape into the gas phase from the membrane. At higher RH, the water activity in the vapor phase is larger, and larger chemical potential leads to extraction of DMSO into the vapor phase according to displacement of the equilibrium:

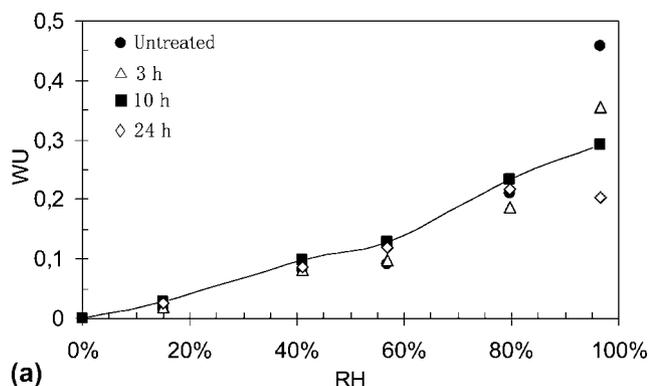

One can observe the onset of extraction around 50% RH in Fig. 5(a) by the sigmoidal shape of the curve. A second sigmoidal can then be observed at even higher RH, around 80% RH [Fig. 5(a)], which might correspond to less hydrophilic decomposition products of DMSO.⁴¹ The release of free space allows subsequently a larger water sorption especially in untreated SPEEK membranes. At higher RH, the WU of all samples increased but much less for crosslinked membranes. The thermal treatment reduced always the amount of sorbed water inside membranes and, consequently, swelling problems at high RH.

From an applicative point of view, thermally treated membranes show an excellent combination of hydration properties: at low RH, they tend to absorb more water facilitating proton conduction, and at high RH, they absorb distinctly less water than untreated SPEEK, reducing thus significantly swelling problems.

E. Chemical water diffusion coefficient

Isothermal water vapor sorption curves of dry samples as function of time at ambient RH are shown in Fig. 6. The untreated membrane shows a clearly higher WU than the treated ones. Chemical diffusion coefficients (D) of water in SPEEK can be calculated from an approximate solution of Fick's second law according to the Eq. (3) when the ratio $m(t)/m_\infty$ is less than 0.5⁴²:

$$\frac{m(t)}{m_\infty} = \frac{4}{L} \sqrt{\frac{Dt}{\pi}} \quad (5)$$

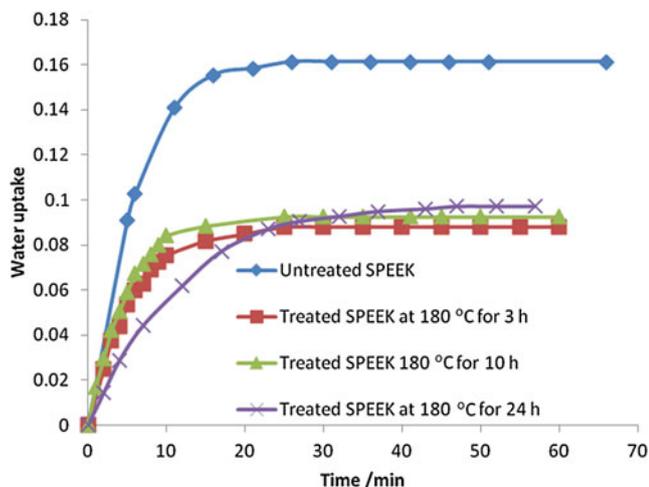


FIG. 6. WU of SPEEK without residual DMSO at ambient RH and temperature as a function of time.

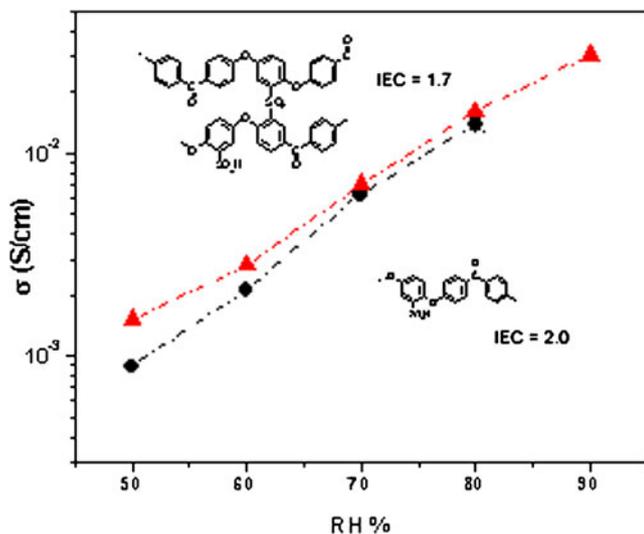


FIG. 7. Proton conductivity of untreated SPEEK (IEC = 2 meq/g, black) and XL SPEEK (IEC = 1.7 meq/g, red, treated at 180 °C for 14 h) at 100 °C as function of RH.

In this equation, $m(t)$ is the WU at time t , m_{∞} the WU after reaching steady state, and L the thickness of SPEEK membranes. As reported in Table IV, the chemical water diffusion coefficient in SPEEK membrane decreased with the annealing time. An increasingly denser three-dimensional network induced by the XL reaction should be responsible for the decrease of D with the annealing time. The observed diffusion coefficients are consistent with the data previously measured for modified SPEEKs.^{42,43} A thermal treatment around 10 h seems to be a nice compromise between hydrolytic/thermal stability and a sufficiently high water diffusion coefficient that is correlated to proton conductivity.

F. Proton conductivity

Figure 7 shows a typical comparison of proton conductivities of untreated and XL SPEEK membranes. There is

a slight increase of proton conductivity of XL SPEEK at low RH, although the loss of some sulfonic acid groups by XL. Furthermore, the proton conductivity of untreated SPEEK is unstable above 80% RH. In contrary, the conductivity of XL membranes is stable and reaches interesting values for future fuel cell applications.

IV. CONCLUSIONS

The mechanical, thermal, and swelling behavior of SPEEK membranes with a high initial DS treated at 180 °C for different times were evaluated. The DXL controlled by changing the heat treatment time, affected the membrane properties. In particular, an intermediate thermal treatment (10 h at 180 °C in our study) was able to provide a promising set of mechanical, thermal, and transport properties. The WU of membranes depends also on the amount of residual DMSO, but in any case, the swelling at high RH is reduced by crosslinking. These satisfying results imply that heat-induced and DMSO-assisted crosslinking is an effective strategy to improve the stability of SAP membranes for PEMFC application.

ACKNOWLEDGMENT

The EU-FP7 (FCH-JU) project “LoLiPEM—Long-life PEM-FCH&CHP systems at temperatures higher than 100 °C” (GA 245339) is gratefully acknowledged for cofunding this work.

REFERENCES

1. T. Higashihara, K. Matsumoto, and M. Ueda: Sulfonated aromatic hydrocarbon polymers as proton exchange membranes for fuel cells. *Polymer* **50**, 5341 (2009).
2. P. Jannasch: Fuel cell membrane materials by chemical grafting of aromatic main-chain polymers. *Fuel Cells* **5**, 248 (2005).
3. G. Zhang, T. Fu, K. Shao, X. Li, C. Zhao, H. Na, and H. Zhang: Novel sulfonated poly(ether ether ketone)s for direct methanol fuel cells usage: Synthesis, water uptake, methanol diffusion coefficient and proton conductivity. *J. Power Sources* **189**, 875 (2009).
4. P.X. Xing, G.P. Robertson, M.D. Guiver, S.D. Mikhailenko, K.P. Wang, and S. Kalitvina: Synthesis and characterization of sulfonated poly(ether ether ketone) for proton exchange membranes. *J. Membr. Sci.* **229**, 95 (2004).
5. J. Kerres, A. Ullrich, F. Meier, and T. Haring: Synthesis and characterization of novel acid-base polymer blends for application in membrane fuel cells. *Solid State Ionics* **125**, 243 (1999).
6. T.A. Zawodzinski, T. Springer, J. Davy, J. Valerie, and S. Gottesfeld: Water transport properties of fuel cell ionomer, in *The Electrochemical Society Proceedings of the Symposium on Modeling of Batteries and Fuel Cells*, Phoenix, AZ, October 13–18, 1991.
7. M.L. Di Vona, S. Licocchia, and P. Knauth: Organic–inorganic hybrid membranes based on sulfonated poly(aryl)-ether-ketones: Correlation between water uptake and electrical conductivity. *Solid State Ionics* **179**, 1161 (2008).
8. L. Li, J. Zhang, and Y. Wang: Sulfonated poly(ether ether ketone) membranes for direct methanol fuel cell. *J. Membr. Sci.* **226**, 159 (2003).

9. H. Hou, M.L. Di Vona, and P. Knauth: Durability study of sulfonated aromatic polymer electrolyte membrane. *ChemSusChem* **4**, 1526 (2011).
10. A. Kusoglu, A.M. Karlsson, M.H. Santare, S. Cleghom, and W.B. Johnson: Mechanical response of fuel cell membranes subjected to a hygro-thermal cycle. *J. Power Sources* **161**, 987 (2006).
11. X.Y. Huang, R. Solasi, Y. Zou, M. Feshler, K. Reifsnider, D. Condit, S. Burlatsky, and T. Madden: Mechanical endurance of polymer electrolyte membrane and PEM fuel cell durability. *J. Polym. Sci., Part B: Polym. Phys.* **44**, 2346 (2006).
12. R. Borup, J. Meyers, J. Pivovar, Y.S. Kim, R. Mukundan, N. Garland, D. Myers, M. Wilson, F. Garzon, D. Wood, P. Zelenay, K. More, K. Stroh, T. Zawodzinski, J. Boncella, J.E. McGrath, M. Inaba, K. Miyatake, M. Hori, K. Ota, Z. Ogumi, S. Miyata, A. Nishikata, Z. Siroma, Y. Uchimoto, K. Yasuda, K. Kimijima, and N. Iwashita: Scientific aspects of polymer electrolyte fuel cell durability and degradation. *Chem. Rev.* **107**, 3904 (2007).
13. S. Mitov, B. Vogel, E. Roduner, H. Zhang, X. Zhu, V. Gogel, L. Jorissen, M. Hein, D. Xing, F. Schonberger, and J. Kerres: Preparation and characterization of stable ionomers and ionomer membranes for fuel cells. *Fuel Cells* **6**, 413 (2006).
14. D.M. Xing, B.L. Yi, F.Q. Liu, Y.Z. Fu, and H.M. Zhang: Characterization of sulfonated poly ether ether ketone/polytetrafluoroethylene composite membrane for fuel cell application. *Fuel Cells* **5**, 412 (2005).
15. H. Voss and K. Friedrich: On the wear behaviour of short-fibre-reinforced peek composites. *Wear* **116**, 1 (1987).
16. Y.H. Lai, M.C. Kuo, J.C. Huang, and M. Chen: Thermomechanical properties of nanosilica reinforced PEEK composites. *Key Eng. Mater.* **351**, 15 (2007).
17. M.L. Di Vona, D. Marani, C. D'Ottavi, M. Trombetta, E. Traversa, I. Beurroies, P. Knauth, and S. Licocchia: A simple new route to covalent organic/inorganic hybrid proton exchange polymeric membranes. *Chem. Mater.* **18**, 69 (2006).
18. J.A. Kerres: Blended and cross-linked ionomer membranes for application in membrane fuel cells. *Fuel Cells* **5**, 230 (2005).
19. J.V. Gasa, R.A. Weiss, and M.T. Shaw: Ionic crosslinking of ionomer polymer electrolyte membranes using barium cations. *J. Membr. Sci.* **304**, 173 (2007).
20. D.X. Luu and D. Kim: Strontium cross-linked sPEEK proton exchange membranes for fuel cell. *Solid State Ionics* **192**, 627 (2011).
21. E. Sgreccia, M. Khadhraoui, C.D. Bonis, S. Licocchia, M.L. Di Vona, and P. Knauth: Mechanical properties of hybrid proton conducting polymer blends based on sulfonated polyetheretherketones. *J. Power Sources* **178**, 667 (2008).
22. Y.W. Chang, E. Wang, G. Shin, J.E. Han, and P.T. Mather: Poly (vinyl alcohol) (PVA)/sulfonated polyhedral oligosilsesquioxane (sPOSS) hybrid membranes for direct methanol fuel cell applications. *Polym. Adv. Technol.* **18**, 535 (2007).
23. H. Li, G. Zhang, J. Wu, C. Zhao, Y. Zhang, K. Shao, M. Han, H. Lin, J. Zhu, and H. Na: A novel sulfonated poly(ether ether ketone) and cross-linked membranes for fuel cells. *J. Power Sources* **195**, 6443 (2010).
24. Z. Zhou, R.N. Dominey, J.P. Rolland, B.W. Maynor, A.A. Pandya, and J.M. Desimone: Molded, high surface area polymer electrolyte membranes from cured liquid precursors. *J. Am. Chem. Soc.* **128**, 12963 (2006).
25. J.A. Kerres: Covalent-ionically cross-linked poly(etheretherketone)-basic polysulfone blend ionomer membranes. *Fuel Cells* **6**, 251 (2006).
26. J. Wang, C. Zhao, G. Zhang, Y. Zhang, J. Ni, W. Ma, and H. Na: Novel covalent-ionically cross-linked membranes with extremely low water swelling and methanol crossover for direct methanol fuel cell applications. *J. Membr. Sci.* **363**, 112 (2010).
27. X. Chen, P. Chen, Z. An, K. Chen, and K. Okamoto: Crosslinked sulfonated poly(arylene ether ketone) membranes bearing quinoxaline and acid-base complex cross-linkages for fuel cell applications. *J. Power Sources* **196**, 1694 (2011).
28. S. Chen, X. Zhang, K. Chen, N. Endo, M. Higa, K. Okamoto, and L. Wang: Cross-linked miscible blend membranes of sulfonated poly(arylene ether sulfone) and sulfonated polyimide for polymer electrolyte fuel cell applications. *J. Power Sources* **196**, 9946 (2011).
29. P. Knauth, H. Hou, E. Bloch, E. Sgreccia, and M.L. Di Vona: Thermogravimetric analysis of SPEEK membranes: Thermal stability, degree of sulfonation and cross-linking reaction. *J. Anal. Appl. Pyrolysis* **92**, 361 (2011).
30. M.L. Di Vona, E. Sgreccia, M. Tamilvanan, M. Khadhraoui, C. Chassigneux, and P. Knauth: High ionic exchange capacity polyphenylsulfone (SPPSU) and polyethersulfone (SPES) cross-linked by annealing treatment: Thermal stability, hydration level and mechanical properties. *J. Membr. Sci.* **354**, 134 (2010).
31. D. Marani, M.L. Di Vona, E. Traversa, S. Licocchia, I. Beurroies, P.L. Lewellyn, and P. Knauth: Thermal stability and thermodynamic properties of hybrid proton-conducting polyaryl etherketones. *J. Phys. Chem. B* **110**, 15817 (2006).
32. M.L. Di Vona, E. Sgreccia, S. Licocchia, G. Alberti, L. Tortet, and P. Knauth: Analysis to temperature-promoted and solvent-assisted cross-linking in sulfonated poly(ether ether ketone) (SPEEK) proton-conducting membranes. *J. Phys. Chem. B* **113**, 7507 (2009).
33. R.C. Weast: *Handbook of Chemistry and Physics*, 61st ed. (CRC Press, Boca Raton, FL, 1981).
34. M.L. Pollio, D. Kitic, and S.L. Resnik: Research note: A w values of six saturated salt solutions at 25°C. Re-examination for the purpose of maintaining a constant relative humidity in water sorption measurements. *Lebensm. Wiss. Technol.* **29**, 376 (1996).
35. P. Knauth, E. Sgreccia, A. Donnadio, M. Casciola, and M.L. Di Vona: Water activity coefficient and proton mobility in hydrated acidic polymers. *J. Electrochem. Soc.* **158**, B159 (2011).
36. E. Sgreccia, J.F. Chailan, M. Khadhraoui, M.L. Di Vona, and P. Knauth: Mechanical properties of proton-conducting sulfonated aromatic polymer membranes: Stress-strain tests and dynamical analysis. *J. Power Sources* **195**, 7770 (2010).
37. H.B. Park, C.H. Lee, J.Y. Sohn, Y.M. Lee, B.D. Freeman, and H.J. Kim: Effect of crosslinked chain length in sulfonated polyimide membranes on water sorption, proton conduction, and methanol permeation properties. *J. Membr. Sci.* **285**, 432 (2006).
38. G. Alberti, R. Narducci, and M. Sganappa: Effects of hydrothermal/thermal treatments on the water-uptake of nafion membranes and relations with changes of conformation, counter-elastic force and tensile modulus of the matrix. *J. Power Sources* **178**, 575 (2008).
39. J.M. Alia, H.G.M. Edwards, and B.M. Kiernan: Raman spectroscopy of benzenesulfonic and 4-toluenesulfonic acids dissolved in dimethylsulfoxide. *Spectrochim. Acta, Part A* **60**, 1533 (2004).
40. Y.S. Li, T.S. Zhao, and W.W. Yang: Measurements of water uptake and transport properties in anion-exchange membranes. *Int. J. Hydrogen Energy* **35**, 5656 (2011).
41. C.F. Bennet: in TECHNICAL BULLETIN (105B) REACTION SOLVENT DIMETHYL SULFOXIDE, Gaylord Chemical Company, L. L. C.
42. M.L. Di Vona, E. Sgreccia, S. Licocchia, M. Khadhroui, R. Denoyel, and P. Knauth: Composite proton-conducting hybrid polymers: Water sorption isotherms and mechanical properties of blends of sulfonated PEEK and substituted PPSU. *Chem. Mater.* **20**, 4327 (2008).
43. K.D. Kreuer, S.J. Paddison, E. Spohr, and M. Schuster: Transport in proton conductors for fuel-cell applications: Simulations, elementary reactions, and phenomenology. *Chem. Rev.* **104**, 4637 (2004).