

Supramolecular Catalysis

International Edition: DOI: 10.1002/anie.201605309
German Edition: DOI: 10.1002/ange.201605309

Reversible Electrochemical Modulation of a Catalytic Nanosystem

Flavio della Sala, Jack L.-Y. Chen, Simona Ranallo, Denis Badocco, Paolo Pastore, Francesco Ricci,* and Leonard J. Prins*

Abstract: A catalytic system based on monolayer-functionalized gold nanoparticles (Au NPs) that can be electrochemically modulated and reversibly activated is reported. The catalytic activity relies on the presence of metal ions (Cd^{2+} and Cu^{2+}), which can be complexed by the nanoparticle-bound monolayer. This activates the system towards the catalytic cleavage of 2-hydroxypropyl-*p*-nitrophenyl phosphate (HPNPP), which can be monitored by UV/Vis spectroscopy. It is shown that Cu^{2+} metal ions can be delivered to the system by applying an oxidative potential to an electrode on which Cu^0 was deposited. By exploiting the different affinity of Cd^{2+} and Cu^{2+} ions for the monolayer, it was also possible to upregulate the catalytic activity after releasing Cu^{2+} from an electrode into a solution containing Cd^{2+} . Finally, it is shown that the activity of this supramolecular nanosystem can be reversibly switched on or off by oxidizing/reducing Cu/Cu^{2+} ions under controlled conditions.

Complexity is emerging as a major theme in chemistry.^[1] Not only does it mark a shift from the study of relatively simple molecules to complex molecular structures similar to those found in nature, but it also marks a shift from the study of single molecules to networks of molecules.^[2–4] Within the subfield of catalysis,^[5] the emergence of nanozymes, defined as nanomaterials with enzyme-like activity, nicely illustrates this development.^[6] Nanozymes are prepared following a bottom-up strategy relying on the use of simple synthetic components for the formation of structures with a size and structural complexity similar to that of enzymes.^[7,8] Their high stability, uniformity, and ease of modification is favoring applications in the fields of sensing,^[9] materials science,^[10] and systems chemistry.^[11] The observation that nanozymes can exhibit an emerging property such as cooperativity is indeed a sign that significant progress has been made in the design of functional complex systems.^[12] However, whereas nature has gained exquisite control over the complex biological machinery by using specific triggers to up- and down-regulate catalytic processes, similar regulatory pathways are still largely inexistent for nanozymes. Herein, we present

a simple setup for the reversible activation and modulation of nanozymes using an electronic input. The electrochemical activation is highly attractive because of its ease of implementation, cleanliness, precision, and rapid response.^[13–16] The availability of this kind of regulatory mechanism will strongly determine the success of chemists in constructing synthetic networks for studying complexity on the systems level.

The main component of our system is Au NP 1, which are gold nanoparticles ($d = 1.5 \pm 0.3$ nm) covered with C9-thiols terminating with a 1,4,7-triazacyclononane (TACN) head group (Figure 1a).^[11] Such nanoparticle-bound TACN moieties are able to coordinate Zn^{2+} -metal ions forming a supra-

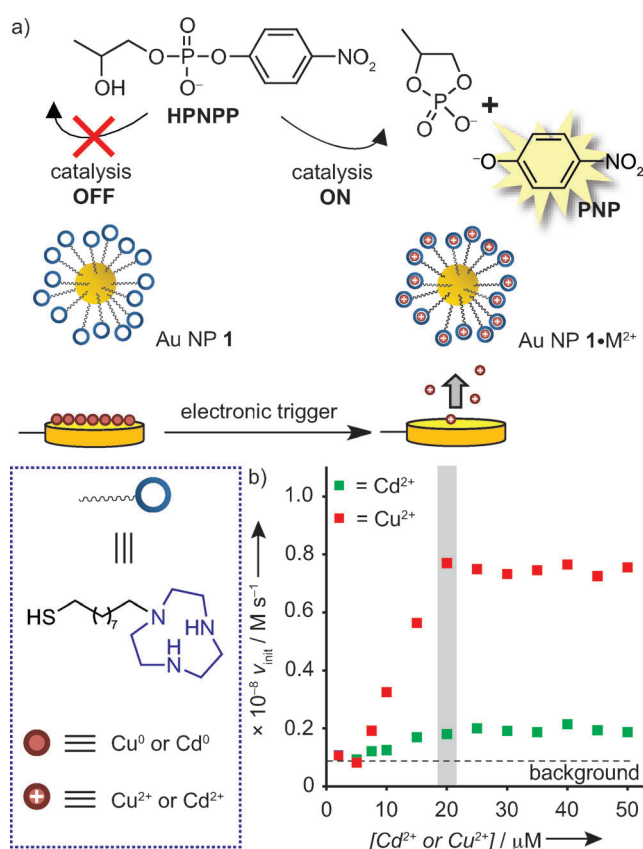


Figure 1. a) Representation of the activation of Au NP 1 through the electrochemically activated release of metal ions from an electrode. b) Initial rate (ν_{init}) of HPNPP transphosphorylation as a function of the concentration of Cu^{2+} (red) or Cd^{2+} (green). The gray bar marks the difference in reactivity of Au NP 1 ($\nu_{\text{init}} = 8.6 (\pm 1.9) \times 10^{-10} \text{ M s}^{-1}$, background), Au NP 1· Cu^{2+} ($\nu_{\text{init}} = 7.7 (\pm 0.9) \times 10^{-9} \text{ M s}^{-1}$), Au NP 1· Cd^{2+} ($\nu_{\text{init}} = 2.0 (\pm 0.3) \times 10^{-9} \text{ M s}^{-1}$) when $[\text{TACN}]/[\text{M}^{2+}]$ ratio is 1:1. Conditions: $[\text{TACN}] = 20 \mu\text{M}$, $[\text{HPNPP}] = 1 \text{ mM}$, $[\text{HEPES}] = 10 \text{ mM}$, pH 7.0, 25 °C.

[*] Dr. F. della Sala, Dr. J. L.-Y. Chen, Dr. D. Badocco, Prof. Dr. P. Pastore, Prof. Dr. L. J. Prins
Department of Chemical Sciences, University of Padova
Via Marzolo 1, 35131 Padova (Italy)
E-mail: leonard.prins@unipd.it

S. Ranallo, Prof. Dr. F. Ricci
Chemistry Department, University of Rome Tor Vergata
Via della Ricerca Scientifica, 00133 Rome (Italy)
E-mail: francesco.ricci@uniroma2.it

Supporting information and the ORCID identification number(s) for the author(s) of this article can be found under:
<http://dx.doi.org/10.1002/anie.201605309>.

molecular catalyst that very efficiently promotes the transphosphorylation of 2-hydroxypropyl-*p*-nitrophenyl phosphate (HPNPP), a common substrate used for mimicking RNA-hydrolysis.^[12]

The role of the nanoparticle support is critical, as the observed rate acceleration is due to the cooperative effect between TACN head groups in close proximity. Limited activity is observed for unbound TACN analogues.^[12] Extensive previous studies have shown that the system displays Michaelis–Menten-like catalytic activity, resulting from the formation of catalytic pockets between two neighboring NP-bound TACN·Zn²⁺-complexes.^[17] For this reason, these systems have also been referred to as nanozymes.^[12] The numerous analogous multivalent systems (both molecular and NP-based) that have been reported require the presence of Zn²⁺ or other metal ions (for example, Cu²⁺, Co³⁺, Ce⁴⁺, Fe³⁺) for catalytic activity.^[18] The observation that Au NP **1** and related systems are poorly active in the absence of metal ions implies that the controlled association and dissociation of metal ions can be used as a regulatory mechanism for catalysis. The low residual activity of non-metalated Au NP **1** presumably originates from the presence of protonated TACN-ligands, at neutral or acidic pH.^[19]

In this study, Cu²⁺ and Cd²⁺ metal ions were deliberately chosen for a number of reasons. Firstly, measurement of the catalytic activity as a function of the amount of Cu²⁺ and Cd²⁺ added to Au NP **1** showed that both metal ions activated the system for catalysis, reaching a maximum when a stoichiometry of 1:1 between the TACN head group and the metal ion was obtained ([TACN] = [Cu²⁺ or Cd²⁺] = 20 μM, Figure 1b). The sharp transition to the plateau-level at this ratio indicates that metal binding occurs under saturation conditions. Importantly, for a 1:1 ratio of [TACN]:[M²⁺], the rate acceleration was significantly higher for Au NP **1**·Cu²⁺ (9 times, red squares) than for Au NP **1**·Cd²⁺ (2.5 times, green squares) when compared to the background (Figure 1b, dashed line). It is pointed out that the absolute activities of the Cu²⁺ and Cd²⁺ systems are much lower compared to that of the analogous Zn²⁺ system that we have studied previously.^[12,17,18] Yet, the more accessible redox-chemistry of Cu and Cd made us focus on these metals, despite the lower catalytic activity. Second, the difference in terms of binding affinity for the TACN group is about six orders of magnitude in favor of Cu²⁺ (log *K*_{TACN·Cu²⁺} = 15.4 and log *K*_{TACN·Cd²⁺} = 9.3),^[20] resulting in complete displacement of Cd²⁺ ions from the NP-bound TACN head groups upon the addition of just an equimolar amount of Cu²⁺ ions. The difference in the activity of the Cu²⁺ and Cd²⁺ systems provides a means to upregulate the catalysis by exchanging Cd²⁺ for Cu²⁺.^[21] Finally, Cu²⁺ and Cd²⁺ metal ions were chosen for their different standard reduction potentials (respectively −0.40 and +0.34 V for Cd²⁺ and Cu²⁺, relative to the standard hydrogen electrode).^[22]

We focused our initial investigations on the electrochemical generation of metal ions from a source in order to switch on catalytic activity. To that purpose, we used a carbon chip^[23] previously coated with a film of Cu⁰. The deposition was carried out by dipping the electrode into an aqueous solution of Cu(NO₃)₂ and by applying a fixed reductive potential of

−1.0 V vs. Ag/AgCl.^[22] Cu²⁺ ions were released from the electrode into a buffered solution containing Au NP **1** and HPNPP by applying a potential oxidative ramp from −0.3 to 0.5 V vs. Ag/AgCl for 60 seconds. We employed square wave voltammetry (SWV; Supporting Information, Figure S4), which quantitatively suggested that about 20 μM of Cu²⁺ was electrochemically released from the electrode.^[22] The absence of NP precipitation and/or aggregation was proven by a combination of UV/Vis spectroscopy, DLS and TEM analyses, confirming that Au NP **1** is stable under the release conditions (Supporting Information, Figures S6–S8). Kinetic measurements (Figure 2) of the initial rate of HPNPP transphosphorylation confirmed that the catalytic system achieved the same activity after the electrochemical release of Cu²⁺ (*v*_{init} = 7.4(±1.2) × 10^{−9} M s^{−1}) as compared to manual addition (*v*_{init} = 7.7(±1.2) × 10^{−9} M s^{−1}). Control experiments confirmed that, without application of the potential, the HPNPP transphosphorylation occurred at a low rate, which is comparable to Au NP **1** in the absence of metal ions (Supporting Information, Figure S5). Quantitative ICP-MS analysis confirmed that the concentration of electrochemically released Cu²⁺ was consistently above the concentration of the NP-bound TACN head groups (20 μM; Supporting Information, Table S1), confirming the results initially suggested by SWV (Supporting Information, Figure S4). It is noted that an excess of Cu²⁺, with regards to the concentration of head groups, does not affect the catalytic activity of the system, as the metal

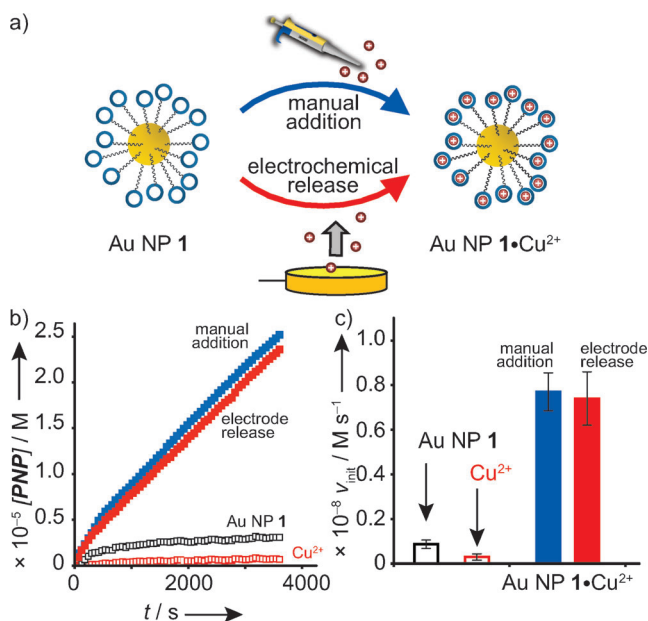


Figure 2. a) Comparison of the efficacy of electrochemical delivery of metal ions as compared to manual addition. b) Example of PNP-formation upon the electrochemical (red) or manual (blue) delivery of Cu²⁺ metal ions to a solution of Au NP **1** ([TACN] = 20 μM) and HPNPP (1 mM). For comparison also the traces for only Au NP **1** and Cu²⁺ are given. c) Averaged initial rates (*v*_{init}; three independent measurements for each trace) for the HPNPP transphosphorylation obtained from the experiments shown in (a). Error bars: ± 1 s.d. Experimental conditions: [HEPES] = 10 mM, pH 7.0, 25 °C. Electrochemical release of Cu²⁺: ramp of potential from −0.3 to 0.5 V vs. Ag/AgCl for 60 s.

ion by itself is not active at these concentrations (see also Figure 1 b). The study was then repeated using Cd instead of Cu. In this case, because of the low oxidation potential of Cd⁰, controlled release of Cd²⁺ from the electrode was not possible. ICP-MS (Supporting Information, Table S1) and kinetic experiments confirmed that Cd²⁺ is spontaneously released from the electrode upon exposure to the solution containing Au NP 1 and HPNPP (Supporting Information, Figure S5). For this reason, the electrode initially covered with Cd was used as a spatially confined metal source in a displacement experiment (Figure 3 a). More specifically, a solution containing Au NP 1 (20 μM) and HPNPP (1 mM) was deposited onto the Cd-loaded electrode, which allowed spontaneous Cd²⁺ release. HPNPP transphosphorylation was then monitored for 30 min by UV/Vis spectroscopy (Figure 3 b, trace I, green). The efficient delivery of Cd²⁺ was evidenced by the observed rate ($v_{\text{init}} = 2.1 \times 10^{-9} \text{ M s}^{-1}$), which

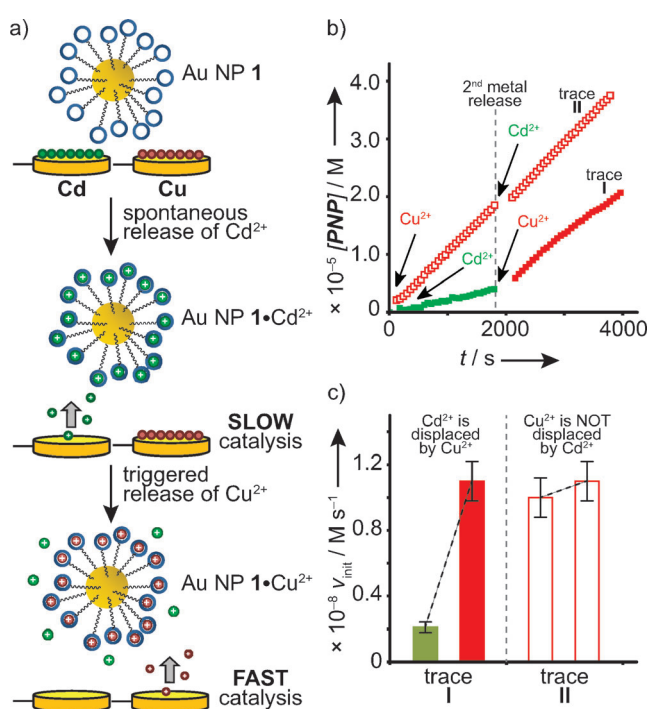


Figure 3. a) Representation of the electrochemical upregulation of catalytic activity. Exposure of Au NP 1 to a Cd⁰-coated electrode results in a weak increase in catalytic activity. Application of an electrochemical trigger to the same solution with a Cu⁰-coated electrode causes the release of Cu²⁺. The released Cu²⁺ displaces Cd²⁺ from the TACN-head groups. b) Representative example of a displacement experiment (all experiments were performed in triplicate; see the Supporting Information, Figure S9). Trace I: initial exposure of Au NP 1 to a Cd-coated electrode followed by exposure (after 30 min) to a Cu-coated electrode to which an oxidative potential was applied. Trace II: initial exposure of Au NP 1 to a Cu-coated electrode with application of an oxidative potential and subsequent exposure (after 30 min) to a Cd-coated carbon chip. PNP-concentration was measured by UV/Vis spectroscopy at 405 nm. Electrochemical release of Cu²⁺: ramp of potential from -0.3 to 0.5 V vs. Ag/AgCl for 60 s. c) Averaged rates of HPNPP transphosphorylation after exposure of Au NP 1 to the different carbon electrodes described in (b). Experimental conditions: [TACN] = 20 μM, [HPNPP] = 1 mM, [HEPES] = 10 mM, pH 7.0, 25 °C. Error bars: ± 1 s.d. calculated from three independent measurements.

corresponded to that of Au NP 1·Cd²⁺ ($v_{\text{init}} = 2.0(\pm 0.3) \times 10^{-9} \text{ M s}^{-1}$ upon manual addition of Cd²⁺). Next, the same solution was re-deposited on a Cu-loaded electrode and a potential ramp from -0.3 to 0.5 V vs. Ag/AgCl was applied, after which the kinetic measurements were continued for an additional 30 minutes. A clear increase in the rate of PNP-formation was observed (v_{init} from 2.1×10^{-9} to $1.1 \times 10^{-8} \text{ M s}^{-1}$, Figure 3 b, trace I, red), which is in full agreement with the value obtained when Cu²⁺ was manually added or electrochemically released in the presence of Au NP 1. This demonstrates the effective displacement of Cd²⁺ by Cu²⁺ from the monolayer resulting in upregulation of catalytic activity. It was important to observe that the rate of PNP-formation did not change at all when Cd²⁺ was released in a solution containing Au NP 1·Cu²⁺ and HPNPP, confirming that Cd²⁺ does not displace Cu²⁺ from the monolayer (Figure 3 b, trace II, empty squares).

The described experiments demonstrate that Cu²⁺ ions can be efficiently delivered through an electrochemical input for the activation of a pre-catalyst. However, full electrochemical control over catalytic activity is achieved only when catalyst activation is a reversible process.^[24,25] The reversibility of the electrochemical activation of the system was investigated using Cu²⁺ (Figure 4 a). As before, Cu²⁺ was released from a prepared electrode into a buffered solution containing Au NP 1 and HPNPP after which the rate of PNP-

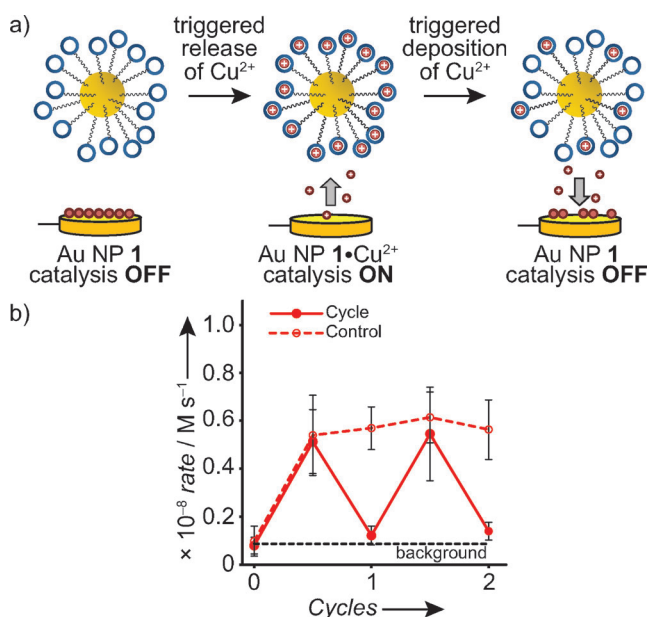






Figure 4. a) Representation of the reversible activation of Au NP 1 driven by the electrochemically controlled release and deposition of Cu²⁺-ions on the electrode. b) Rate of HPNPP transphosphorylation after two cycles of activation/deactivation of Au NP 1. The control experiment indicates the observed rate when Au NP 1 was just activated once by the electrochemical release of Cu²⁺ at the start of the experiment. Experimental conditions: [TACN] = 20 μM, [HPNPP] = 1 mM, [HEPES] = 10 mM, pH 7.0, 25 °C. Error bars: ± 1 s.d. calculated from three independent measurements. Electrochemical release of Cu²⁺: ramp of potential from -0.3 to 0.5 V vs. Ag/AgCl for 60 s. Electrochemical deposition of Cu²⁺: fixed potential of -1.0 V vs. Ag/AgCl for 10 min.


Communications



Supramolecular Catalysis

F. della Sala, J. L.-Y. Chen, S. Ranallo,
D. Badocco, P. Pastore, F. Ricci,*
L. J. Prins*    

Reversible Electrochemical Modulation of
a Catalytic Nanosystem

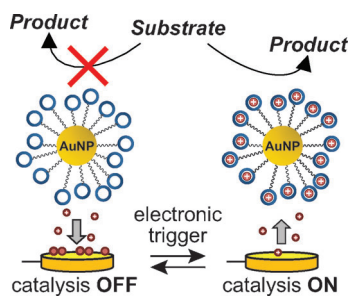

Hop on, hop off: Metal ions are reversibly released from an electrode to regulate the activity of a gold nanoparticle catalyst (see picture). The system catalyzes the cleavage of 2-hydroxypropyl-*p*-nitrophenyl phosphate and the formation of *p*-nitrophenolate can be monitored by UV/Vis spectroscopy.